

APPLICATION OF TAGUCHI METHOD FOR OPTIMIZING SURFACE ROUGHNESS IN CNC TURNING OF EN 8 STEEL

N. Sathiya Narayanan, M. Ganesan, V. Prem Kumar, P. Vijayakumar, N. Baskar
*Department of Mechanical Engineering, Saranathan College of Engineering,
Trichy, Tamil Nadu, INDIA Pincode- 620012*

Abstract--Turning operation is the basic metal removal process; during this process heat is generated between the work piece and cutting tool which affects the surface finish of the work piece. The advantage of using this CNC turning process is to reduce the cost and also enhance the quality of the finished component. In this experimental work conducted on EN8 material using CNC Lathe with SINUMERIK 802D Control System with variable cutting speed of 60 rpm, 80 rpm and 100 rpm based on the L9 orthogonal array. The turning parameters such as spindle speed, feed rate and depth of cut was selected and investigated at three different levels to study the effect on surface roughness. The surface roughness of the work piece is measured using TR 1900 SURFACE ROUGHNESS TESTER. The optimum level of turning parameters was determined by using Taguchi design of experiments. The statistical methods of signal to noise ratio (S/N) and analysis of variance (ANOVA) were applied to investigate the effects of turning process parameters on surface roughness. Confirmation test with the optimal levels of cutting parameters shows that the optimized value of SR falls within 95% confidence level

Index Terms- Turning Process, Design of Experiments, EN 8 Steel, Surface roughness.

I. INTRODUCTION

The turning process parameters such as spindle speeds, feed rates and depth of cuts are the main factors that affect the surface roughness. The main objective of this experimental work is to find the optimum machining parameters for better surface quality of the work pieces.

Shreemoy Kumar Nayak et al (2014) investigated the influence of machining parameters namely cutting speed, feed and depth of cut on turning of AISI 304 stainless steel using ISO P30 grade uncoated cemented carbide insert and adopted L27 orthogonal array to measure the characteristics of

machinability such as material removal rate (MRR), Cutting force (F_c) and surface roughness (R_a). The machining parameters are optimized using gray relational analysis.

Ali R. Yildiz (2013) used evolutionary based optimization technique of artificial bee colony algorithm for selecting the optimal cutting parameters in multi-pass turning operations and compared with previously published results. Dorian M. D'Addona et al (2013) determined the optimal cutting parameters during turning process using genetic algorithm for reducing the production cost and time.

L.B. Abhang et al (2012) carried out the turning process in EN31 steel alloy using tungsten carbide inserts by varying the cutting parameters namely feed rate, depth of cut, and lubricant temperature to observe the effects on surface finish. Khaider Bouacha et al (2014) conducted an experimental study of hard turning of AISI 52100 bearing steel, with CBN tool by using response surface methodology (RSM) to find the relationship between process parameters and performance characteristics. The results show that the cutting speed exhibits maximum influence on abrasive tool wear and depth of cut affects strongly the cutting forces.

Arshad Noor Siddiquee et al(2014) focused on optimizing deep drilling parameters based on Taguchi method for minimizing surface roughness by conducting experiments on CNC lathe machine using solid carbide cutting tool on material AISI 321 austenitic stainless steel and determined the machining parameter which significantly affects the surface roughness and also the percentage contribution of individual parameters.

Murat Sarıkaya et al (2014) used design of experiments to study the effect of turning parameters such as cooling condition, cutting speed, feed rate and depth of cut on arithmetic average roughness (R_a) and average maximum height of the profile (R_z) by turning of AISI 1050 steel. The mathematical model for surface roughness is created using response surface

methodology and concluded that feed is the most effective parameter on the surface roughness.

Mustafa Günay et al (2013) performed experimentation in the CNC lathe using ceramic and cubic boron nitride (CBN) cutting tools on Ni-Hard materials with two different hardness levels 50 HRC and 62 HRC. Taguchi L18 Orthogonal array design of experiments is used for finding out the optimum turning parameters and also studied the effect of parameters on surface roughness.

T. Rajasekaran et al (2013) examined the process parameters such as cutting speed, feed and depth of cut for machining carbon fiber reinforced polymer material and studied the effect of these parameters on surface roughness. N. Senthilkumar et al (2014) investigated the effect of machining parameters such as cutting speed, feed rate and depth of cut, geometrical parameters of cutting insert shape, relief angle and nose radius on flank wear, Surface Roughness (SR) & Material Removal Rate (MRR) were optimized using Taguchi based grey relational analysis.

Dipti Kanta Das et al (2014) dealt with investigations on surface roughness during hard machining of EN 24 steel with the help of coated carbide insert. The process parameters are optimized by using Grey based Taguchi approach and it was found that the feed is the most dominant parameter for surface roughness. C.K. Umesh et al (2014) investigated the turning parameters namely cutting speed, feed rate and depth of cut resulting in an optimal value of feed force, tangential force and surface roughness for machining EN-19 steel with an coated carbide tool insert.

Ramazan Çakıroğlu et al (2013) evaluated the cutting parameters on drill bit temperature in drilling process of Al7075 work piece with coated carbide drill tool using Taguchi method. Empirical equation is derived using regression analysis for the drill bit temperature and the obtained equation results were compared with experimental results. The empirical equations results indicated a good agreement with experimental results.

P. Venkataramaiah et al (2014) studied the influence of feed rate and tool geometry on cutting force during turning using Taguchi Method and Fuzzy Logic. Series of turning experiments are conducted by using Taguchi Experimental Design on Aluminium work piece with the HSS cutting tools. The cutting forces are recorded for different angle geometry and feed rate.

From the literature survey, the identification of machining problem for EN8 steel rods which cannot be tackled using conventional technique because of the following problems occurs in turning process Poor chip breaking, High work hardened, Transformation induced plasticity; Affect the passive surface, Machining distortion.

The above problems are to overcome during CNC turning to achieve better surface quality and with close dimensional accuracy.

II. EXPERIMENTAL DETAILS

When the number of processing parameters increases, the classical methods of experimental design are too complex and large numbers of experiments are to be carried out. To overcome these issues, Taguchi method used an orthogonal array to investigate the process parameters with only a few experiments. In this experimental work, experiments were carried out with three independent factors namely cutting speed, feed rate and depth of cut at three levels each. Here a standard L9 orthogonal array was used. The various cutting parameters and their levels are shown in Table 1 and Table 2 shows standard L9 orthogonal array

TABLE 1 CUTTING PARAMETERS AND LEVELS

Levels	Cutting speed (rpm)	Feed rate (mm/rev)	Depth of cut (mm)
Low	60	0.2	2
Medium	80	0.3	3
High	100	0.4	4

TABLE 2 ORTHOGONAL ARRAY L9 OF TAGUCHI EXPERIMENT DESIGN

Experiment	Cutting speed (rpm)	Feed rate (mm/rev)	Depth of cut (mm)
1	1	1	1
2	1	2	2
3	1	3	3
4	2	1	2
5	2	2	3
6	2	3	1
7	3	1	3
8	3	2	1
9	3	3	2

A. Work piece material

In this experimental work, EN 8 steel is used to find out the optimum turning parameters for surface roughness (SR). Initially a EN8 rod of 25 mm diameter

and 70mm length is taken and 30 mm length is placed inside the chuck of the CNC machine, the remaining 40mm were turned for each trail.

TABLE 3 CHEMICAL COMPOSITION OF EN 8 STEEL

Elements	Weight %
C	0.36
Mn	0.66
Si	0.27
S	0.016
P	0.020

TABLE 4 MECHANICAL PROPERTIES OF EN 8 STEEL

Sl. No	Mechanical Property	Range
1	Max Stress	700-850 N/mm ²
2	Yield Stress	465 N/mm ²
3	Elongation	16%
4	Impact KCV	28 J
5	Hardness	201-255 Inell

Table 3 and 4 shows the chemical composition and mechanical properties of EN 8 Steel material.

B. Cutting inserts

Carbide insert of ISO designation CNMG 120408 (80° diamond shaped inset) without chip breaker geometry has been used for experimentation.

C. Experimental Procedure

The turning tests on the work piece were conducted under dry conditions on a CNC lathe SINUMERIK (802 D) which have a maximum spindle speed of 5000 rpm and maximum power of 16 kW. The surface roughness of the work pieces is measured using TR 1900 Surface Roughness Tester

Figure 1& 2 shows the CNC lathe machine SINUMERID (802D) and TR 1900 Surface Roughness Tester respectively. Table 5 shows the specifications of CNC Lathe.

TABLE 5: MACHINE SPECIFICATION OF CNC LATHE

Sl.No	Specifications	Dimensions/Range
1	Max. Swing Over Carriage	180mm
2	Distance between centers	220mm
3	Height of the center	165mm
4	Spindle bore diameter	40mm
5	Spindle speed	5000 rpm



Fig. 1 CNC lathe SINUMERIK (802 D)



Fig. 2 TR1900 Surface Roughness Tester.

TABLE 6: S/N RATIOS OF EXPERIMENTAL RESULTS FOR SR

Cutting Speed (rpm)	Feed (mm/rev)	Depth of cut (mm)	Surface Roughness(Ra) (µm)			Average Surface Roughness (Ra) (µm)	S/N Ratio (dB)
			Trail 1	Trail 2	Trail 3		
60	0.2	2	2.705	2.472	2.137	2.438	-7.7406
60	0.3	3	2.191	2.169	2.481	2.28	-7.1586
60	0.4	4	1.813	1.83	1.839	1.827	-5.2347
80	0.2	3	1.223	1.462	1.614	1.433	-3.1249
80	0.3	4	1.298	1.133	1.436	1.289	-2.2051
80	0.4	2	1.896	1.706	1.717	1.773	-4.9741
100	0.2	4	0.839	0.836	0.873	0.849	1.4218
100	0.3	2	1.104	1.218	1.135	1.152	-1.2291
100	0.4	3	1.025	1.049	1.311	1.128	-1.0461

III.RESULTS AND DISCUSSION

The experimental trails were conducted according to the standard L9 Orthogonal array. The use of Taguchi method for experimental design is to determine significant parameters which affect the surface roughness.

After determining the signal-to-noise (S/N) ratio of the experimental results, a statistical analysis using analysis of variance (ANOVA) was conducted to reveal significant machining parameters that affect the surface roughness. MINI TAB 17.0 software was used for Taguchi’s Method and for analysis of variance (ANOVA).

A. Regression equations

The mathematical predictive regression models developed for the SR as shown in equations (1)

$$SR = 4.55 - 0.0285 A - 0.013 B - 0.233 C \quad (1)$$

where ‘A’ represents cutting speed, ‘B’ represents feed rate, ‘C’ represents depth of cut.

B. Analysis of Surface Roughness (SR)

Surface roughness of the work piece is tested using surface roughness tester on three different places

of the work piece and the average of the values is used.

$$S/N_s = 10 \log \left(\frac{1}{n} \sum_{i=1}^n y_i^2 \right) \quad (2)$$

In general, there are three different quality characteristics in S/N ratio analysis namely “Larger is the better”, “Nominal is the best” and “Smaller is the better”. For each level of turning process parameters signal-to-noise ratio is calculated based on smaller is better S/N analysis for surface roughness.

TABLE 7: RESPONSE TABLE S/N RATIOS FOR SR

Level	Cutting speed (rpm)	Feed Rate (mm/rev)	Depth of Cut (mm)
1	-6.7114	-3.1479	-4.6480
2	-3.4347	-3.5309	-3.7766
3	-0.2845	-3.7517	-2.0060
Delta	6.4249	0.6038	2.6460
Rank	1	3	2

Table 7 shows that cutting speed is given with rank 1, depth of cut given with rank 2 and feed rate given with rank 3. It meant that cutting speed is plays dominant role in roughness of the surface.

TABLE 8: RESULTS OF ANOVA FOR SURFACE ROUGHNESS

Source	D.o.f	Sum of square	Mean square	F value	Contribution%
Cutting speed (rpm)	2	1.9708	0.9854	40.45	83.78
Feed rate (mm/rev)	2	0.0001	0.0001	0	-
Depth of cut (mm)	2	0.3327	0.1663	6.83	14.14
Error	2	0.0487	0.0243	-	2.07
Total	8	2.3522	-	-	100

To analyze the effects of cutting speed, feed rate and depth of cut on surface roughness ANOVA is used. ANOVA is a statistical tool to determine and analyze the individual interactions of all control factors. From the table 7 & 8, cutting speed had a dominant effect (83.78%) on surface roughness whereas the other actors were found small comparing with cutting speed.

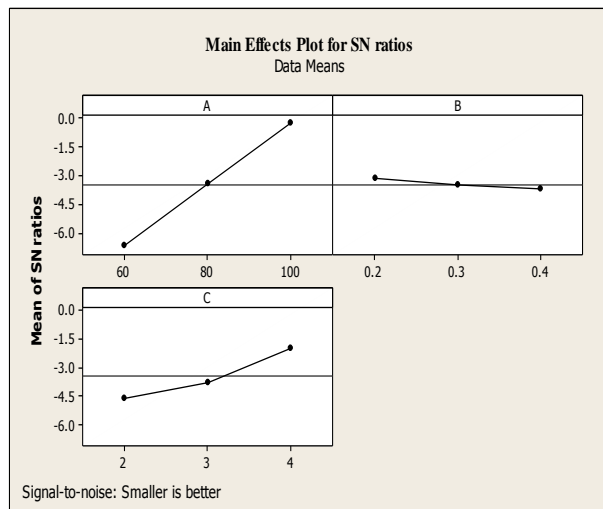


Fig. 3 Main effects plot for S/N ratio of SR.

Figure 3 shows the main effect plots based on S/N ratio (smaller is better) for SR. The optimum parameters are level 3 for cutting speed, level 1 for feed rate and level 3 for depth of cut.

TABLE 9 CONFIRMATION RUN OF SR

Response	Optimal parameters	Predicted Value	Experimental Value
SR(μm)	A3B1C3	0.7706	0.849

Table 9 shows the optimal setting from the Taguchi's approach gives an appropriate combination as cutting speed of 100 rpm, feed rate of 0.2mm/rev and depth of cut of 4mm. The predicted value from regression models for SR is 0.7706(μm). The experimental value gives 0.849 (μm) for SR for the same parameter combinations.

IV.CONCLUSIONS

In this work, Taguchi's methodology has been utilized to determine the optimal parameters which affecting the quality of the work piece. Based on the results presented the conclusions are as follows:

The use of a L9 orthogonal array, with three control parameters at three levels required only nine work pieces to conduct the experimental portion, which is less than required for a full factorial design.

Cutting speed played a dominant role on surface roughness. The parameters considered in the experiments are optimized to attain better surface finish. The best setting of input process parameters for defect free turning within the selected range is cutting speed of 100rpm, feed rate of 0.2mm/min and depth of cut of 4mm.

A parameter design gives the optimum condition of the controlled parameters, as well as a predictive equation. A verification procedure is then performed, which indicates that the selected parameters and predictive equation were accurate to within the limits of the measurement.

REFERENCES

- [1] Shreemoy Kumar Nayak, Jatin Kumar Patro, Shailesh Dewangan, Soumya Gangopadhy "Multi-objective Optimization of Machining Parameters During Dry Turning of AISI 304 Austenitic Stainless Steel Using Grey Relational Analysis" Procedia Materials Science Volume 6, 2014, Pages 701–708
- [2] Stefan Velchev, Ivan Kolev, Krasimir vanov Simeon Gechevski "Empirical models for specific energy consumption and optimization of cutting parameters for minimizing energy consumption during turning" Journal of Cleaner Production. Volume 80, 1 October 2014, Pages 139–149.

- [3] Ali R. Yildiz “Optimization of cutting parameters in multi-pass turning using artificial bee colony-based approach” *Information Sciences*, Volume 220, January 2013, Pages 399–407.
- [4] P. Suresh, K. Marimuthu, S. Ranganathan, T. Rajmohan “Optimization of machining parameters in turning of Al-SiC-Gr hybrid metal matrix composites using grey-fuzzy algorithm” *Transactions of Nonferrous Metals Society of China* Volume 24, Issue 9, September 2014, Pages 2805–2814
- [5] Doriana M. D’Addona, Roberto Teti “Genetic Algorithm-based Optimization of Cutting Parameters in Turning Processes”, *Procedia CIRP* Volume 7, 2013, Pages 323–328
- [6] L.B. Abhang, M. Hameedullah “Optimization of Machining Parameters in Steel Turning Operation by Taguchi Method” *Procedia Engineering* Volume 38, 2012, Pages 40–48
- [7] Fabrício José Pontes, Anderson Paulo de Paiva, Pedro Paulo Balestrassi, João Roberto Ferreira, “Optimization of Radial Basis Function neural network employed for prediction of surface roughness in hard turning process using Taguchi’s orthogonal arrays”, *Expert Systems with Applications*, Volume 39, Issue 9, July 2012, Pages 7776–7787
- [8] Khaider Bouacha, Mohamed Athmane Yallese, Samir Khamel, Salim Belhadi “Analysis and optimization of hard turning operation using cubic boron nitride tool”, *International Journal of Refractory Metals and Hard Materials*, Volume 45, July 2014, Pages 160–178
- [9] Rastee D. Koyee, Rocco Eisseler, Siegfried Schmauder “Application of Taguchi coupled Fuzzy Multi Attribute Decision Making (FMADM) for optimizing surface quality in turning austenitic and duplex stainless steels”, *Measurement*, Volume 58, December 2014, Pages 375–386
- [10] Arshad Noor Siddiquee, Zahid A. Khan, Pankul Goel “Optimization of Deep Drilling Process Parameters of AISI 321 Steel Using Taguchi Method”, *Procedia Materials Science*, Volume 6, 2014, Pages 1217–1225
- [11] Murat Sarıkaya, Abdulkadir Güllü “Taguchi design and response surface methodology based analysis of machining parameters in CNC turning under MQL”, *Journal of Cleaner Production*, Volume 65, 15 February 2014, Pages 604–616
- [12] Lohithaksha M. Maiyar, R. Ramanujam, K. Venkatesan, J. Jerald “Optimization of Machining Parameters for end Milling of Inconel 718 Super Alloy Using Taguchi based Grey Relational Analysis”, *Procedia Engineering*, Volume 64, 2013, Pages 1276–1282
- [13] Avisha Chowdhury, Rajat Chakraborty, Debarati Mitra, Dipa Biswas “Optimization of the production parameters of octyl ester biolubricant using Taguchi’s design method and physico-chemical characterization of the product”, *Industrial Crops and Products*, Volume 52, January 2014, Pages 783–789
- [14] Mustafa Günay, Emre Yücel “Application of Taguchi method for determining optimum surface roughness in turning of high-alloy white cast iron”, *Measurement*, Volume 46, Issue 2, February 2013, Pages 913–919
- [15] T. Rajasekaran, K. Palanikumar, S. Arunachalam “Investigation on the Turning Parameters for Surface Roughness using Taguchi Analysis”, *Procedia Engineering*, Volume 51, 2013, Pages 781–790
- [16] N. Senthilkumar, T. Tamizharasan, V. Anandkrishnan “Experimental investigation and performance analysis of cemented carbide inserts of different geometries using Taguchi based grey relational analysis” *Measurement*, Volume 58, December 2014, Pages 520–536
- [17] Dipti Kanta Das, Ashok Kumar Sahoo, Ratnakar Das, B.C. Routara “Investigations on Hard Turning Using Coated Carbide Insert: Grey based Taguchi and Regression Methodology” *Procedia Materials Science*, Volume 6, 2014, Pages 1351–1358
- [18] M. Durairaj, D. Sudharsun, N. Swamynathan “Analysis of Process Parameters in Wire EDM with Stainless Steel Using Single Objective Taguchi Method and Multi Objective Grey Relational Grade” *Procedia Engineering*, Volume 64, 2013, Pages 868–877.
- [19] R. Manjunatha, C.K. Umesh “Optimization of Tangential Force, Feed Force and Surface Roughness Using Taguchi Technique in Turning Operation” *Procedia Materials Science*, Volume 5, 2014, Pages 1685–1691
- [20] Ramazan Çakıroğlu, Adem Acır “Optimization of cutting parameters on drill bit temperature in drilling by Taguchi method” *Measurement*, Volume 46, Issue 9, November 2013, Pages 3525–3531
- [21] A. Del Prete, T. Primo, R. Franchi “Super-Nickel Orthogonal Turning Operations Optimization” *Procedia CIRP*, Volume 8, 2013, Pages 164–169
- [22] P. Venkataramaiah, K. DharmaReddy P. Meramma “Analysis on Influence of Feed Rate and Tool Geometry on Cutting Forces in Turning Using Taguchi Method and Fuzzy Logic” *Procedia Materials Science*, Volume 5, 2014, Pages 1692–1701
- [23] Apurba Kumar Roy, Kaushik Kumar “Effect and Optimization of Various Machine Process Parameters on the Surface Roughness in EDM for an EN41 Material Using Grey-Taguchi” *Procedia Materials Science*, Volume 6, 2014, Pages 383–390